

1a. REPORT SECURITY CLASSIFICATION

Unclassified

2a. SECURITY CLASSIFICATION

AD-A222 025

ON PAGE

ADDITIONAL MARKINGS

None

DISTRIBUTION/AVAILABILITY OF REPORT

Unlimited

2b. DECLASSIFICATION/DOWNGRADING SCHEDULE

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

interim technical report #36

5. MONITORING ORGANIZATION REPORT NUMBER(S)

6a. NAME OF PERFORMING ORGANIZATION

Department of Chemistry

6b. OFFICE SYMBOL
(if applicable)

7a. NAME OF MONITORING ORGANIZATION

Office of Naval Research

6c. ADDRESS (City, State, and ZIP Code)

Massachusetts Institute of Technology
77 Mass. Avenue, Bldg. 6-335
Cambridge, MA 02139

7b. ADDRESS (City, State, and ZIP Code)

Chemistry Division
800 N. Quincy Street
Arlington, VA 222178a. NAME OF FUNDING/SPONSORING
ORGANIZATION

Office of Naval Research

8b. OFFICE SYMBOL
(if applicable)

9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER

N00014-84-K-0553

8c. ADDRESS (City, State, and ZIP Code)

Chemistry division
800 N. Quincy Street
Arlington, VA 22217

10. SOURCE OF FUNDING NUMBERS

PROGRAM
ELEMENT NO.PROJECT
NO.TASK
NO.WORK UNIT
ACCESSION NO.

051-579

11. TITLE (Include Security Classification)

Characterization of a "Solid-State" Microelectrochemical Diode...

12. PERSONAL AUTHOR(S)

L. Laventis, M.O. Schloh, M.J. Natan, J.J. Hickman and M.S. Wrighton

13a. TYPE OF REPORT

technical interim

13b. TIME COVERED

FROM 5/89 TO 5/90

14. DATE OF REPORT (Year, Month, Day)

5/16/90

15. PAGE COUNT

45

16. SUPPLEMENTARY NOTATION

Prepared for Publication in Chemistry of Materials

17. COSATI CODES

FIELD

GROUP

SUB-GROUP

18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

Microelectrode, acid solid-state electrolyte, WO₂
polyaniline

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

See Attached Sheet

BEST
AVAILABLE COPYDTIC
ELECTE
MAY 25 1990
S E D

20. DISTRIBUTION/AVAILABILITY OF ABSTRACT

☐ UNCLASSIFIED/UNLIMITED ☐ SAME AS RPT.☐ DTIC USERS

21. ABSTRACT SECURITY CLASSIFICATION

Unlimited

22a. NAME OF RESPONSIBLE INDIVIDUAL

Mark S. Wrighton

22b. TELEPHONE (Include Area Code)

617-253-1597

22c. OFFICE SYMBOL

ABSTRACT

The functionalization of an array of eight, closely-spaced ($\sim 1.2 \mu\text{m}$) Pt or Au microelectrodes each $\sim 50 \mu\text{m}$ long, $2 \mu\text{m}$ wide, and $0.1 \mu\text{m}$ thick with redox active WO_3 and polyaniline and the electrochemical characterization of the WO_3 /polyaniline junction is reported. Chips consisting of microfabricated WO_3 covering three of the available eight microelectrodes have been analyzed by Auger electron spectroscopy. The remaining five microelectrodes are available for further derivatization with polyaniline or can function as counterelectrodes. By placing a counterelectrode and a Ag quasi-reference electrode directly on the microchip and by coating the assembly with a thin film of poly(vinyl alcohol)/ H_3PO_4 solid polymeric electrolyte the electrochemical system becomes self-contained. The solid polymer electrolyte is a good room temperature H^+ conductor only when exposed to a H_2O -containing atmosphere. Complex impedance studies show as much as a 10^3 change in H^+ conductivity from H_2O -saturated to H_2O -free gaseous atmosphere above the polymer electrolyte. The changes in conductivity of WO_3 upon reduction or polyaniline upon oxidation allow demonstration of solid state microelectrochemical transistors with these materials. The combination of WO_3 and polyaniline on the chip allows demonstration of a microelectrochemical diode.

Office of Naval Research
Contract NOOO14-84-K-0553
Task No. 051-597
Technical Report #36

Characterization of a "Solid-State" Microelectrochemical Diode
Employing a Poly(vinyl alcohol)/Phosphoric Acid Solid-State
Electrolyte: Rectification at Junctions between WO_3 and Polyaniline

by

Nicholas Leventis, Martin O. Schloh, Michael J. Natan
James J. Hickman, and Mark S. Wrighton

Prepared for Publication
in

Chemistry of Materials
Massachusetts Institute of Technology
Department of Chemistry
Cambridge, MA 02139

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input checked="" type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Special	
A-1	

Reproduction in whole or in part is permitted for any purpose of the
United States Government.

This document has been approved for public release and sale; its
distribution is unlimited.

[Prepared for publication as an article in
Chemistry of Materials]

**Characterization of a "Solid-State"
Microelectrochemical Diode Employing a Poly(vinyl
alcohol)/Phosphoric Acid Solid-State Electrolyte:
Rectification at Junctions between WO₃ and Polyaniline**

Nicholas Leventis, Martin O. Schloh, Michael J. Natan, James
J. Hickman, and Mark S. Wrighton*

*Department of Chemistry
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139*

* Address correspondence to this author.

ABSTRACT

The functionalization of an array of eight, closely-spaced ($\sim 1.2 \mu\text{m}$) Pt or Au microelectrodes each $\sim 50 \mu\text{m}$ long, $2 \mu\text{m}$ wide, and $0.1 \mu\text{m}$ thick with redox active WO_3 and polyaniline and the electrochemical characterization of the WO_3 /polyaniline junction is reported. Chips consisting of microfabricated WO_3 covering three of the available eight microelectrodes have been analyzed by Auger electron spectroscopy. The remaining five microelectrodes are available for further derivatization with polyaniline or can function as counterelectrodes. By placing a counterelectrode and a Ag quasi-reference electrode directly on the microchip and by coating the assembly with a thin film of poly(vinyl alcohol)/ H_3PO_4 solid polymeric electrolyte the electrochemical system becomes self-contained. The solid polymer electrolyte is a good room temperature H^+ conductor only when exposed to a H_2O -containing atmosphere. Complex impedance studies show as much as a 10^3 change in H^+ conductivity from H_2O -saturated to H_2O -free gaseous atmosphere above the polymer electrolyte. The changes in conductivity of WO_3 upon reduction or polyaniline upon oxidation allow demonstration of solid state microelectrochemical transistors with these materials. The combination of WO_3 and polyaniline on the chip allows demonstration of a microelectrochemical diode.


We wish to report the preparation and characterization of a "solid-state" microelectrochemical diode based on the contact of microlithographically patterned WO_3 and electrochemically polymerized polyaniline on arrays of closely-spaced ($\sim 1.2 \mu\text{m}$) microelectrodes. The chip is subsequently covered with a thin film ($\sim 20 \mu\text{m}$) of poly(vinyl alcohol)/ H_3PO_4 solid-state electrolyte. Poly(vinyl alcohol)/ H_3PO_4 , a H_2O -swollen proton-conducting polymer blend of poly(vinyl alcohol) and H_3PO_4 , has recently been proposed as the electrolyte in connection with a H_2 sensing device.¹ The polymer blend is deemed an interesting solid-state electrolyte for room temperature applications,¹ because of its high ionic conductivity.

Murray and co-workers pioneered² the preparation and characterization of redox polymer bilayers to demonstrate electrochemical diodes. Our studies of WO_3 and polyaniline provide an example of such a system where both of the redox layers could become good electronic conductors upon forward bias of a diode assembly. Accordingly, the current passing through the diode may be qualitatively larger than that for electrochemical diodes based on conventional redox polymers such as the diode from polyvinylferrocene/polyviologen previously reported.³


Microelectrode arrays consisting of eight individually addressable Pt or Au microelectrodes, each $\sim 50 \mu\text{m}$ long, $\sim 2.2 \mu\text{m}$ wide, $\sim 0.1 \mu\text{m}$ thick, have previously been used in our laboratory for the study of redox active polymers and

inorganic materials.⁴ By taking advantage of solid-state electrolytes based on poly(ethylene oxide) (PEO),⁵ poly(vinyl alcohol) (PVA),⁶ and poly[bis(2-(2-methoxyethoxy)-ethoxy)phosphazene] (MEEP),⁷ we have demonstrated microelectrochemical systems where all ancillary components of the system (counter electrode and reference electrode) are confined onto the chip. We have previously found⁶ that the electrochemical switching properties of polyaniline using poly(vinyl alcohol)/H₃PO₄ electrolyte are essentially the same as in liquid electrolytes, except the switching speed is lower. In this report we wish to detail the electrochemical response of WO₃ using the poly(vinyl alcohol)/H₃PO₄ electrolyte medium and show that polyaniline and WO₃ can be exploited together to yield novel electrochemical systems.

Three of the five microelectrochemical systems characterized in this paper are shown in Scheme I. The thrust of our experiments is to thoroughly characterize the WO₃ and polyaniline microelectrochemical systems shown in Scheme I. These individual systems, Scheme IA and IB, are referred to as microelectrochemical transistors. The characterization is key to understanding how WO₃ and polyaniline can be used together to produce other electrical functions such as the self-referencing transistors, Scheme IC, and diode-like behavior, Scheme II. By "self-referencing" in Scheme IC we mean that one redox material is used as a reference for the other such that an applied

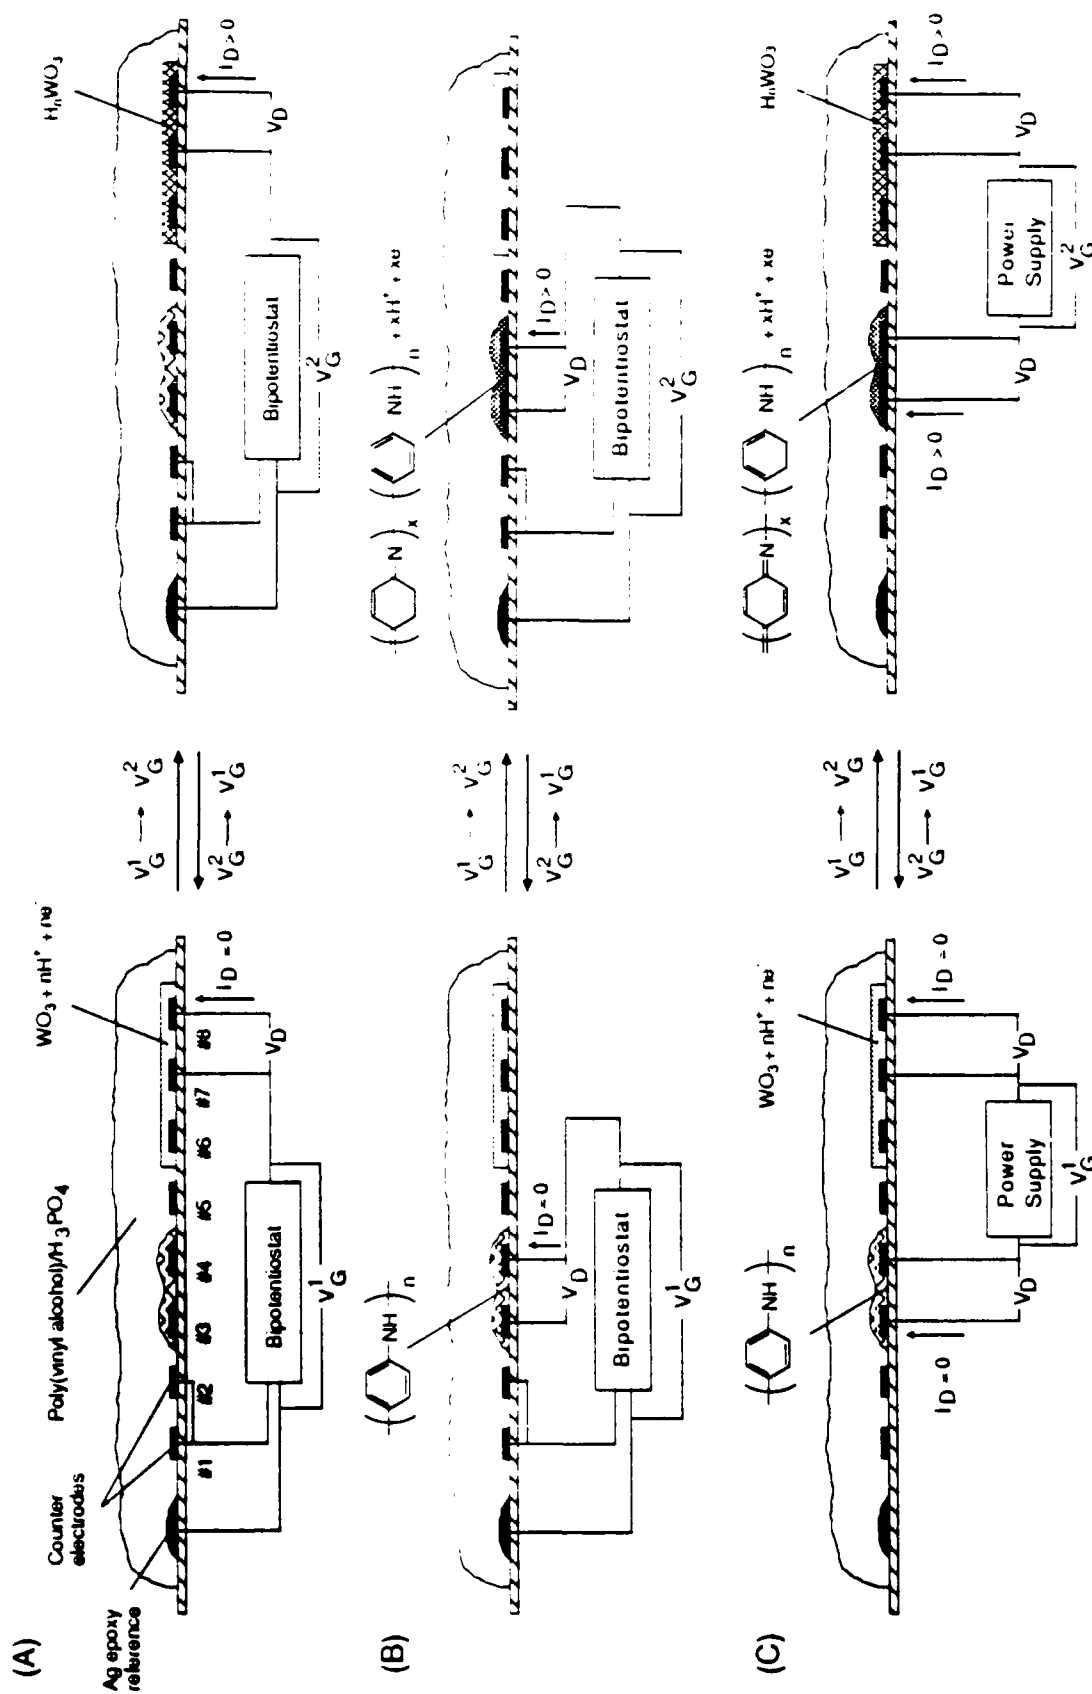

Scheme 1. Cross-sectional views of "solid-state" microelectrochemical devices. (A) WO₃-based transistor. (B) Polyaniline-based transistor. (C) WO₃ and polyaniline self-referencing transistor (cf. text).

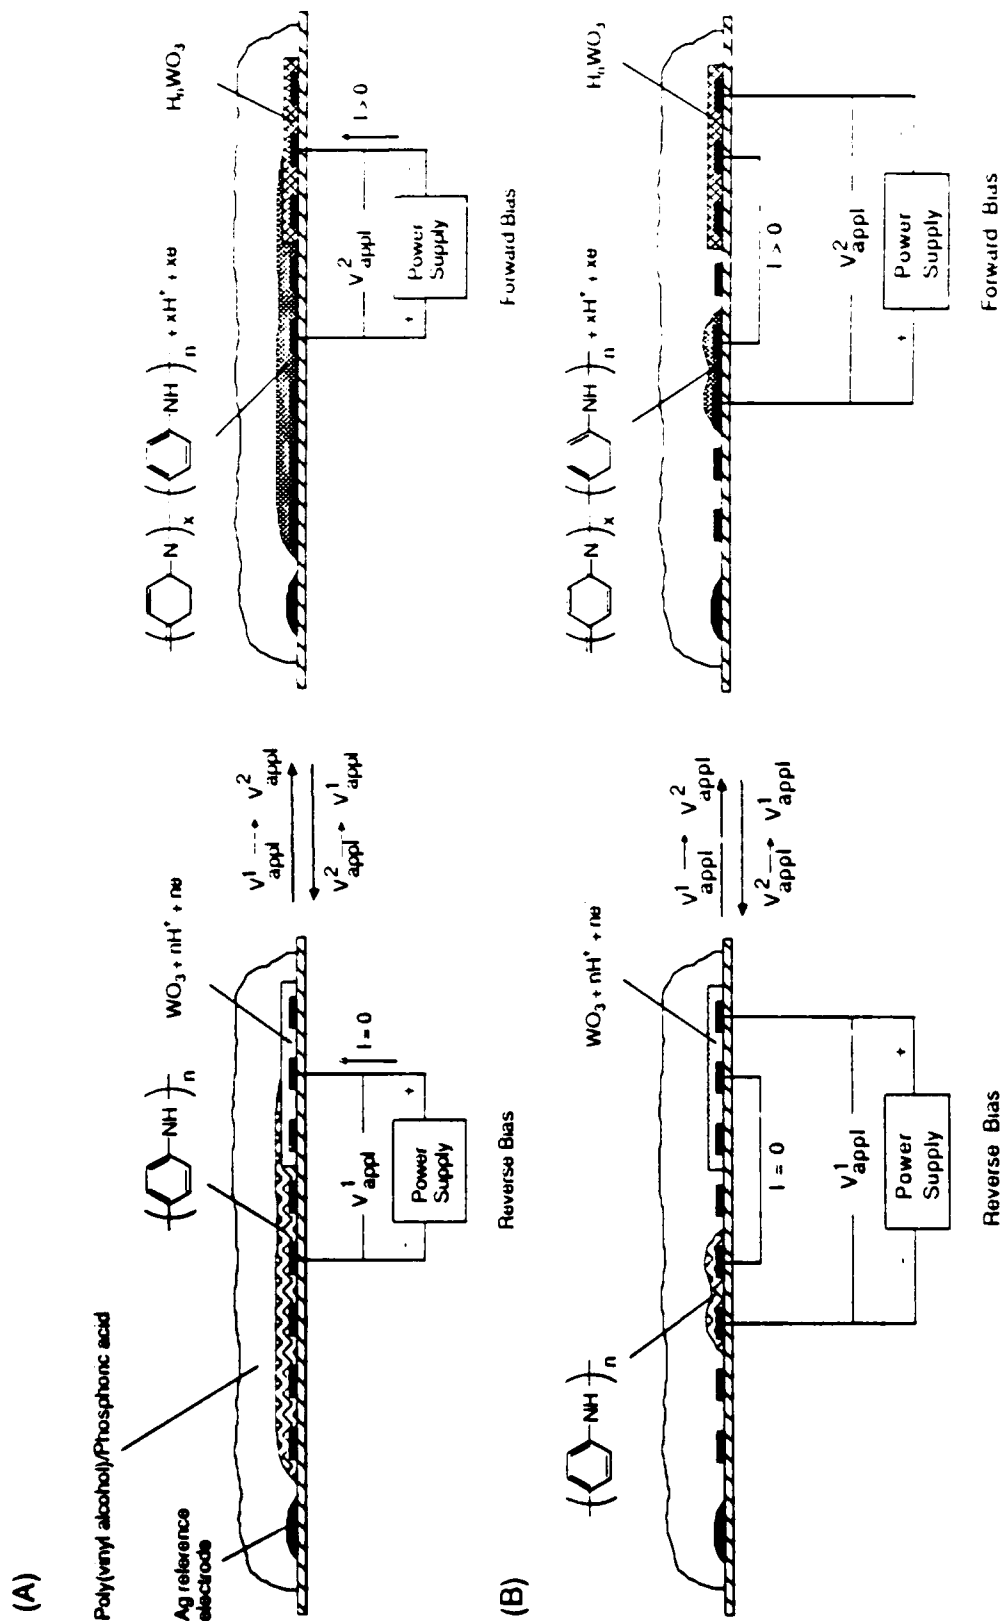

Scheme II. Microelectrochemical diode based on WO_3 and polyaniline. (A) WO_3 and polyaniline are in direct contact forming a WO_3 /polyaniline junction. (B) WO_3 and polyaniline are connected through an external wire.

potential change, $V_{G1} \rightarrow V_{G2}$, will result in simultaneous switching of both transistors.

Scheme IA illustrates the methodology for the electrochemical characterization of WO_3 confined to electrodes #6-8. Basically, the relative conductivity as a function of electrochemical potential is determined by varying the gate potential, V_G , while monitoring the drain current, I_D , at a small fixed drain potential, V_D . Previous work has shown that reduction of WO_3 to H_nWO_3 in aqueous solution yields a highly conducting material.^{4c} Polyaniline confined to microelectrodes #3 and #4, Scheme IB, can be characterized in an analogous way.^{4d,6} The difference is that polyaniline is an insulator when reduced and becomes a conductor when oxidized.^{4d,6} Thus, WO_3 and polyaniline have complementary behavior suggesting the viability of the self-referencing transistors in Scheme IC where the application of a voltage in a two-terminal mode renders both materials conducting.

Polyaniline and WO_3 are also regarded as electrochemical energy storage materials and can be used in combination as illustrated in Scheme IC to yield a surface storage device. The reversible charge and discharge shown in Scheme IC is strictly analogous to charge and discharge of a battery. This type of assembly of complementary redox materials on working and counterelectrode is commonly used in research on so-called electrochromic smart windows, which are of current interest for energy conservation in buildings and cars.⁸

For the system shown in Scheme IC, the self-referencing transistors, where the charge passed in changing V_G results in simultaneous switching of two transistors, it is important to recognize the need to have the proper ratio of polyaniline and WO_3 to achieve maximum conductivity in each material. To illustrate, if there is a very large amount of polyaniline and a small amount of WO_3 , the WO_3 will be reduced completely and becomes conducting while the polyaniline is only fractionally oxidized and will not be conducting. Establishing the relationships between potential, state of charge and conductivity for both WO_3 and polyaniline is, therefore, critical to rational design of microelectrochemical systems.

Turning now to the combination of polyaniline and WO_3 to form microelectrochemical diodes, consider the remaining two systems described in this article, Scheme II. The electrical behavior of the WO_3 /polyaniline junction in Scheme IIA may be understood in terms of the electrochemistry involved in both materials comprising the diode. For instance, if an electrical potential, V_{appl} , is applied across the WO_3 /polyaniline junction such that the WO_3 -derivatized microelectrode is biased positively with respect to the polyaniline-derivatized microelectrode (reverse bias), no current should pass through the junction, in part because WO_3 is insulating when oxidized and polyaniline is insulating when reduced. However, the key to rectification is that reduction of WO_3 by reduced polyaniline is not feasible

thermodynamically. Upon forward bias (negative lead to WO_3), WO_3 can be reduced to a conducting tungsten bronze, H_nWO_3 , and polyaniline is oxidized and also conducting. At the WO_3 /polyaniline junction, charge is transported through the interface by the thermodynamically favored redox reaction between oxidized polyaniline and reduced H_nWO_3 . The threshold voltage, V_T , of the WO_3 /polyaniline-based solid-state microelectrochemical diode, is approximately the difference in potential for oxidizing polyaniline and reducing WO_3 . This difference is also the approximate switching potential for the self-referencing transistors, Scheme IC.

Importantly, we find that an actual junction between WO_3 and polyaniline is not required in order to demonstrate electrochemical rectification. A diode-like current-voltage characteristic can be obtained by simply externally connecting two separated WO_3 -derivatized and polyaniline-derivatized microelectrodes with a wire, Scheme IIB. This contacting scheme has been introduced earlier by Murray and co-workers in their studies of redox bilayer materials.² The hardwire connection scheme greatly simplifies the assembly of microelectrochemical diodes, because a good electrical contact between diverse redox materials, e.g. conducting polymers and redox-active oxides, is not essential for rectification.

EXPERIMENTAL SECTION

Microelectrode Modification. The microfabrication process for derivatizing microelectrodes with WO_3 has previously been described.⁹ The individual devices were mounted on TO-8 headers (Schott Electronics) with Ag-epoxy (epoxy technology) and encapsulated with clear epoxy (Hydrosol Division, Dexter Corporation). Subsequently, the WO_3 -based device was cleaned in an O_2 plasma (100 mtorr, 200W) for 4-5 min. The remaining microelectrodes were electrochemically cleaned by repeated potential excursions between -1.5 and -2.0 V vs. saturated calomel electrode (SCE) in 0.1 M K_2HPO_4 . Polyaniline was selectively deposited on only two microelectrodes of the array by cycling the potential of the electrodes between -0.1 V to +0.85 V vs. SCE in 0.1 M aniline (Aldrich) 0.5 M NaHSO_4 /0.6 M H_2SO_4 solution, while all remaining electrodes were kept at -0.1 V vs. SCE. In order to make devices with a WO_3 /polyaniline connection all electrodes were scanned between -0.1 V to +0.85 V vs. SCE, except the WO_3 -derivatized electrodes which were not under potential control. For the independent characterization of the two redox materials confined to the microelectrodes of the solid-state device two bare Pt microelectrodes were used as the counterelectrodes and a small spot of Ag epoxy (close to the microelectrode array area) served as a quasi-reference electrode. The whole device active area was then covered with a drop of an aqueous solution containing 0.2 mM poly(vinyl alcohol) (Polysciences), $\text{MW} = 1.33 \times 10^5$, 99% hydrolyzed, and 0.15 M

H₃PO₄. The solid state device is completed by evaporation of the H₂O at 35 °C for 24 h. The resulting transparent film contains one H₃PO₄ per four poly(vinyl alcohol) repeat units. In order to estimate the typical thickness resulting from one drop of aqueous poly(vinyl alcohol)/H₃PO₄ solution, we placed a drop on a microscope slide, dried it, and determined its thickness by surface profilometry to be ~20 μm.

AC Impedance Analysis. A Solartron 1255 HF Frequency Response Analyzer combined with a Solartron 1286 Electrochemical Interface was used for impedance measurements. The ac excitation was 20 mV and spectra were taken in the frequency range between 1 Hz and 100 kHz. A simple impedance cell was constructed by scratching a narrow groove through a thin (0.1 μm) Pt layer evaporated onto a glass slide. The electrolyte solution was then cast on top of the two electrode open sandwich impedance cell and dried at room temperature. The open-face arrangement of the two ~1 cm² electrodes was used to facilitate the rapid hydration and dehydration of the electrolyte film. The geometry is thus not ideal for absolute measurement, but gives excellent relative resistances. AC impedance measurements using clean microelectrode arrays were attempted but apparently the impedance change in the solid electrolyte is obscured by the considerable impedance of the microelectrode array and connection leads. Regular gas wash bottles were used to repeatedly hydrate and dry the Ar gas or air which was blown

over the impedance cell. The impedance cell was housed in a glass flask.

Auger Surface Analysis. The analysis by scanning Auger spectroscopy of a conducting material on an insulator has previously been complicated by differential charging. This problem was overcome by carefully placing a thin coating of silver paint on the insulating layer around the array and grounding the electrodes at the same time. The paint was dried for ~5 min in air and then in an oven at 90 °C for 15 min. Finally the sample was grounded with Ag paint to a piece of Cu tape which, in turn, was grounded to the spectrometer.

Auger spectra were obtained with a PDP 11/04-controlled Physical Electronics (Perkin Elmer) Model 590 scanning Auger microprobe spectrometer (SAM) employing a 0.8 μm , 80-100 nA, 10 keV electron beam for excitation and a cylindrical mirror analyzer (CMA) for detection. For mapping, the electron beam energies were chosen to maximize the peak-to-peak separation of the derivatized Auger spectra. The difference between the magnitudes of the peak-to-peak separation corresponded to signal intensity. The signals were segregated into three levels of varying intensity and displayed on a 160 x 160 array. Surface sputtering of the sample prior to analysis to remove carbon-containing impurities was accomplished using a 2 keV, 5.0 nA/cm² Ar⁺ beam.

Electrochemical Equipment. Electrochemical experiments were carried out with use of a Pine Instruments Model RDE-4

bipotentiostat. Voltammetric traces were recorded on a Kipp and Zonen Model BD 91 XYY' recorder with the zero suppression option and a time base function. A Nicolet Model 4094B Digital Oscilloscope with Model 4570 digitizer and Model F-43 disk drive plug-ins was used for the high frequency characterization experiments. For the potential variation we used either the linear output of a PAR Model 175 Programmer or the sinusoidal waveform of the internal oscillator output of a PAR Model 5204 lock-in amplifier.

RESULTS AND DISCUSSION

a. Surface Characterization by Auger Spectroscopy.

Using a combination of photolithographic and dry etching processes a thin film of polycrystalline WO_3 can be patterned to selectively cover a fraction of eight individually addressable and closely-spaced ($\sim 1.2 \mu\text{m}$ apart) Pt microelectrodes ($\sim 50 \mu\text{m}$ long, $2.5 \mu\text{m}$ wide, and $0.1 \mu\text{m}$ thick).⁹ The modified microelectrode array can be characterized by Auger electron spectroscopy, which provides surface elemental analysis of the surface, to establish the success of the microfabrication process.

Figure 1A shows a low resolution SEM micrograph indicating the region of a chip covered by WO_3 . Figure 2 shows three Auger electron spectra taken on different areas of such a WO_3 -coated chip. The spectra are shown for the WO_3 -coated region, Figure 2A, for a bare Pt microelectrode, Figure 2B, and for the insulating trench around the microelectrodes, Figure 2C. The important information from these spectra is that (1) only W and O are present in the area where WO_3 is claimed to be confined; and (2) the Pt electrodes show no evidence of W. The Pt electrodes show Pt, Si, and O in the survey, Figure 2B, but the Si and O are due to the fact that the beam size has a slightly larger diameter than the width of the microelectrodes, so that Si and O from the substrate are also detected.

A collection of Auger element maps obtained for a WO_3 -coated chip is included in Figure 1. The maps represent

the distribution of elements over the surface of the chips. In order to map W, the primary peak at 1736 eV was used. Due to overlapping Auger electron emission energies it was necessary to use the third most intense peak for Pt, at 1967 eV, and the second most intense peak for Si at 1619 eV. The W and Pt images are virtually noise-free and look very clean, Figures 1B and 1D. However, the use of the secondary peak for Si gave a noisy image, Figure 1C, owing to poor signal-to-noise. Overall, both the Auger survey spectra and the Auger element maps clearly indicate that WO_3 has been confined to three microelectrodes of the array. Equally important in our present work is the fact that the remaining five microelectrodes are free of WO_3 and are available for further derivatization with polyaniline by polymerization of aniline.

b. Characterization of Poly(vinyl alcohol)/ H_3PO_4

Solid-State Electrolyte. Poly(vinyl alcohol)/ H_3PO_4 mixtures have recently attracted interest due to their high ionic conductivity at room temperature when dried to a film.¹ The mixtures are prepared by dissolving poly(vinyl alcohol) and H_3PO_4 in a ratio of 4:1 polymer repeat units per acid molecule in hot H_2O .¹ Upon drying this mixture a solvent-swollen solid polymeric electrolyte film is obtained, whose conductivity depends on the amount of H_2O in the poly(vinyl alcohol)/ H_3PO_4 film.

We have used standard ac impedance techniques¹⁰ to determine the extent of change of ionic conductivity in the

electrolyte film upon variation of the atmosphere from H₂O-free to H₂O-saturated. Figure 3 shows the ac impedance spectrum for a "dry" poly(vinyl alcohol)/H₃PO₄ film. This spectrum features a large semicircle and a spur. This response agrees with the data reported by Petty-Weeks and Polak^{1b} and is often encountered for solid electrolytes.¹⁰ The intersect of the low frequency end of the semicircle with the real axis yields the ionic resistance R of the electrolyte for this particular impedance cell. The specific resistivity, ρ , can be calculated if the separation of the electrodes, l, and the electrode area, A, is known: $\rho = (R \times A)/l$. We can only estimate the actual A/l, owing to the open-face electrode structure, but our dry state specific resistivities are in reasonable accord with data of Polak.^{1b} The ionic resistance of a "dry" film is $\sim 2.2 \times 10^6 \Omega$ or $\rho = 4.4 \times 10^6 \Omega\text{cm}$. Upon switching the gas flow to H₂O-saturated Ar gas (or H₂O-saturated air) the ac impedance spectrum, Figure 3, exhibits only a poorly developed semicircle. The resistance of the electrolyte in its "wet" state is significantly lower than the "dry" state, on the order of 800 Ω or $\rho = 1.6 \times 10^3 \Omega\text{cm}$. The presence of a separate phosphoric acid/water phase, which is responsible for the H⁺ conduction in the H₂O swollen polymer film has been reported.^{1b} The important point is that the conductivity of the poly(vinyl alcohol)/H₃PO₄ film can be reversibly and rapidly ($\sim 30\text{s}$) modulated by changing the H₂O content of the ambient gas. Since the dry film is a high resistance ionic

conductor, reduction of WO_3 or oxidation of polyaniline in this medium will be sluggish in comparison to that in the hydrated film. Accordingly, our characterizations of the five electrochemical systems shown in Scheme I and II have been generally carried out in H_2O -saturated gases.

c. Electrochemical Characterization of WO_3 and Polyaniline in Poly(vinyl alcohol)/ H_3PO_4 Solid

Electrolyte. Optical micrographs of two modified microelectrode arrays are shown in Figure 4. The device in the upper half of the Figure consists of three WO_3 -coated microelectrodes adjacent to one bare microelectrode next to which are two polyaniline-coated microelectrodes. A Ag spot (out of the field of view) is used as the quasi-reference electrode and the two remaining microelectrodes on the left side of the microelectrode array are shorted together and used as the counterelectrode. The chip shown in the upper half of Figure 4 can be used to characterize all systems shown in Scheme I and the hardwired diode shown in Scheme IIB. In the lower half of Figure 4, polyaniline has been grown on all five, previously bare, microelectrodes and overcoats the WO_3 -coated microelectrodes. This array can be used to characterize the system in Scheme IIA.

Cyclic voltammetric characterization of the array depicted in the top half of Figure 4 is shown in Figure 5. Microelectrodes #3 and #4 exhibit electrochemistry typical of polyaniline.^{4d,6} The fact that the shape of the cyclic voltammogram for electrodes #3 and #4 scanned separately is

the same as when both electrodes are scanned together at all scan rates indicates that polyaniline electrically connects the two electrodes. The electrochemical response of WO_3 -coated microelectrodes, #6, #7, and #8 of the array is similar to the electrochemistry observed for WO_3 in aqueous acid electrolyte, and we concluded that reduction of WO_3 to H_nWO_3 occurs in the solid H^+ conductor.^{4c} Examination of the polyaniline and WO_3 upon oxidation and reduction by optical microscopy shows the green coloration expected for oxidized polyaniline and the blue coloration for reduced WO_3 .

d. Solid State Microelectrochemical Transistors Based on WO_3 and Polyaniline. The ability to reversibly reduce WO_3 suggests the possibility of a WO_3 -based solid state transistor as previously demonstrated for polyaniline. As for polyaniline-coated microelectrodes, H_2O -dependent electrochemical behavior is also observed for WO_3 under a poly(vinyl alcohol)/ H_3PO_4 solid electrolyte film.

Microelectrochemical transistors based on WO_3 -functionalized microelectrodes work on the principle that the conductivity of the redox material is a function of the state of charge (cf. Scheme IA). For the case of a WO_3 -based device, the oxidized form of WO_3 is an insulator, and the reduced, proton-intercalated form, H_nWO_3 , is an electronic conductor. Therefore, as the gate potential, V_G^1 , which controls the state of charge, is moved from an oxidizing potential to a reducing potential, V_G^2 , a drain current, I_D , will flow between the microelectrodes (#7 and #8 in Scheme IA) for a

fixed drain potential, V_D . Figure 6 includes a typical plot of drain current, I_D , vs. gate voltage, V_G . The switching characteristics of WO_3 in hydrated poly(vinyl alcohol)/ H_3PO_4 are essentially the same as the electrochemical response found in aqueous acidic electrolytes.^{4c,9} By switching the atmosphere surrounding the WO_3 -based device from H_2O -saturated Ar to dry Ar, the device cannot be "switched-on" by sweeping to a negative potential, and remains an insulator until H_2O is introduced into the Ar atmosphere. This is an expected result in view of the fact that the mobility of the intercalating species, H^+ , is impeded in the dry solid-state electrolyte. Hence reduction of WO_3 to H_nWO_3 cannot be effected. Along the same line of reasoning, when the WO_3 device is already in its "switched-on" or conducting state, H_nWO_3 , and the atmosphere surrounding the device is changed from H_2O -saturated to dry gas the device stays in the conducting form even when V_G is moved to a potential where H_nWO_3 should be oxidized to WO_3 .

Figure 6 confirms that polyaniline- and WO_3 -based transistors on the same chip, Figure 4, addressed independently yield characteristics identical to those obtained when the polyaniline or WO_3 are on different chips. Thus, the fabrication processes yield a chip which has two microelectrochemical transistors. WO_3 is "switched on" at some negative potential, V_G , depending on the availability of protons and its conductivity reaches a plateau as the material is driven to more a negative V_G . Polyaniline, on

the other hand, becomes conducting at positive V_G , and its conductivity reaches a maximum value at +0.45 V vs. Ag quasi-reference.⁶ The independent characterization of WO_3 and polyaniline against a common reference electrode, i.e. the Ag quasi-reference, clearly shows that there is a region of gate potential, about 200 mV wide, in which neither material is appreciably conducting.

The simultaneous switching of both the polyaniline- and WO_3 -based transistors is possible if one redox material is used as the reference for the other, Scheme IC. The potential at which both materials become conducting or the turn-on potential, V_T , should be about 200 mV as predicted by the difference in V_G where polyaniline and WO_3 become conducting, Figure 6. The value of V_T from the self-referencing transistor is thus characteristic of the two switching materials employed in the system. However, the simultaneous switching of the two materials also depends on balancing the amounts present such that the electrons removed from polyaniline to result in a conductor will be adequate to effect sufficient reduction of WO_3 to render it conducting. Integration of cyclic voltammograms like those in Figure 5 and comparison of the potential limits with the I_D - V_G plots for the individual transistors in Figure 6 can be used to gauge whether the materials are adequately balanced. In our experiments we are typically dealing with $\sim 10^{-7}$ C/cm² in order to effect switching of either the WO_3 - or polyaniline-based transistors. Figure 8 shows that a single applied potential

can be used to effect simultaneous switching of the WO_3 - and polyaniline-based transistors on the same chip. In this system a small drain potential, V_D , applied across a pair of microelectrodes coated with WO_3 or polyaniline (cf. Scheme IC) allows simultaneous monitoring of the conductivity of each material as a function of V_G . As illustrated in Figure 7, I_D in both transistors becomes significant for $V_G > 200$ mV, as expected.

e. Characterization of Rectifying Devices by Interfacing Polyaniline with WO_3 . The optical micrograph in Figure 4B shows a microelectrochemical system where polyaniline has been grown over some large fraction of the WO_3 -coated microelectrodes ensuring intimate contact between the two redox materials. The electrical characterization of a two-terminal device based on this junction, Scheme IIA, shows that large current densities, on the order of A's/cm², can be driven across the junction in only one direction. The turn-on potential is about 200 mV, consistent with results from the independent characterization of the two materials and the self-referencing device.

The rectification behavior observed may be understood in terms of the electrochemistry involved in each of the two materials comprising the diode junction. The key to the diode-like current-potential curve is that oxidized polyaniline can oxidize the H_nWO_3 , but reduced polyaniline cannot reduce WO_3 owing to the difference in their redox potentials. Thus, the redox process occurring at the

WO₃/polyaniline interface is sufficiently thermodynamically downhill in only one direction that charge transport across the interface is effectively unidirectional.

In order to achieve a microelectrochemical diode WO₃ and polyaniline do not have to be in physical contact, Scheme IIB. In Figure 8 the two-terminal current-voltage characteristic of a microelectrochemical device is shown where WO₃ and polyaniline are not in physical contact with each other. As expected, no steady-state current passes through the two-terminal device when the circuit between WO₃ and polyaniline is not completed. However, a simple external hardwire connection as schematically represented in Scheme IIB restores a complete electrical circuit and rectifying behavior is found.

An important difference between the diode devices in Figure 8, and the transistors, Figures 6 and 7, is the rather large currents are observed at forward bias for the diodes compared to the modest currents observed during I_D vs. V_G characterizations of the transistors. For the diodes the bias across the junction is much larger (1-2 V) compared to the small, 25 mV, value of V_D applied across two microelectrodes in the transistors. Secondly, the limiting thickness of the WO₃ layer for the diode is not 1.2 μm , i.e. spacing between microelectrodes, but $\sim 0.3 \mu\text{m}$ which is the thickness of the layer of WO₃ over which the polyaniline is grown. In the case of the hardwire connection diode, Figure 8, the observed current through the device is somewhat lower

than that for the case of a physical connection between WO_3 and polyaniline because the circuit is completed through a longer current path involving two polyaniline-covered and two WO_3 -covered microelectrodes both spaced $\sim 1.2 \mu\text{m}$ apart, thus adding a resistive element to the circuit.

Interestingly, the diode devices like that shown in Figure 4B can be evaluated with and without a hardwire connection in parallel with the physical contact between the WO_3 and polyaniline. The hardwire contact is obviously independent of the kinetics for charge transport across the physical contact between the two materials. If the charge transport across the physical contact limited the diode current, the hardwire connection would result in a larger diode current under forward bias. We find no effect on the diode current in such a test and conclude that the diode current is limited by the charge transport properties of the bulk materials. From the data in Figures 6 and 7 the H_nWO_3 and oxidized polyaniline show similar maximum conductivity. Thus, the diode currents are more or less equally dependent on the WO_3 and polyaniline.

The maximum forward bias of the diodes is about +2.0 V, because the devices decay quickly at +2.3 V to +2.4 V forward bias, as can be concluded from an irreversible decline of forward current. When the diodes are reverse-biased only a small current is observed, on the order of 1-10 μA at 1.0 V in Figure 8. This may be due to leakage currents through imperfections of the WO_3 layer contacted with polyaniline. A

reverse bias breakdown occurs at about 2.0 V. Devices remaining at that voltage for long times also tend to lose their ability to "switch on" under forward bias. Examination by optical microscopy reveals that upon breakdown, either under forward or reverse bias, the polyaniline films have peeled off the microelectrodes and gas bubbles, presumably H_2 or O_2 , are trapped in the solid electrolyte just above the array.

The current-voltage characteristic shown in Figure 8 is a steady state curve in the sense that each data point is obtained after several minutes, typically 5 min, in order to allow the device to equilibrate under the new bias. If an alternating potential between the extremes of +1.0 V and -1.0 V is fed into the two-terminal device and the current is recorded, the rectification factors with respect to frequency can be determined. In Figure 9, the results of such an experiment are shown for a diode with the physical contact between the WO_3 and polyaniline. A sinusoidal potential variation with 1 Hz frequency is illustrated. Defining the ratio $I_{forward}/I_{reverse}$ as the rectification factor of the device at a given frequency a measure of the response time can be gathered, Table I. The main point is that the current response of the WO_3 /polyaniline junction is sluggish. Even at only 1 Hz, $I_{forward}/I_{reverse}$ equals 8.8 which is already about 50 times lower than the steady state rectification factor, indicating a fairly large delay in the discharge of the two materials. Interestingly, even at 1 kHz the devices

retain some rectification ability, as is demonstrated by the value of the rectification factor which is still slightly larger than unity (~ 1.4). While polyaniline switches rapidly between its insulating and conducting states, up to 1 kHz in liquid electrolyte,¹¹ and up to 100 Hz in poly(vinyl alcohol)/H₃PO₄ solid electrolyte,⁴ the kinetics of WO₃ redox chemistry are found to be more sluggish. Switching speeds on the order of only several Hz even in aqueous acid^{4c} have been reported. Therefore, we attribute the sluggish switching of the diode device to the slow response of WO₃ and not to the slow response of polyaniline.

CONCLUSION

Both WO_3 and polyaniline have been confined in a controlled manner onto a microelectrode array consisting of eight individually addressable microelectrodes. Both the amount and spatial distribution of the redox materials can be controlled to yield various electrochemical systems yielding characteristics which stem from the properties of the individual components. The redox materials can either be placed separately (to yield transistors or diodes) or in physical contact (to yield diodes) on the microelectrode array. The poly(vinyl alcohol)/ H_3PO_4 solid-state polymer electrolyte is used to cover the assembly of derivatized microelectrodes. The switching properties of the resulting "solid-state" devices have been characterized and a microelectrochemical, solid-state rectifying device based on the interface of WO_3 with polyaniline has been assembled. Interestingly, the two redox materials do not have to be in physical contact as long as there is a hardwire connection between them. The hardwire connection procedure may be useful in constructing a myriad of diode devices based on redox materials with widely different properties where a good, direct connection between the materials may be difficult to achieve. Additionally, the hardwire approach allows a chip to be reconfigured after being derivatized with different redox materials. For example, an array of eight microelectrodes could be functionalized with four redox materials to give four individually addressable transistors

or be hardwired to give six different diodes. Obviously, the reconfiguration of diodes having physical junctions would be difficult. However, the maximum number of independently operating diodes on the eight electrode array with hardwire connections is two requiring three redox materials, whereas physical junctions would allow as many as four independently operating diodes using four different materials.

ACKNOWLEDGEMENTS

We thank Professor D. R. Sadoway for the use of his AC impedance equipment. We would like to thank the Office of Naval Research and the Defense Advanced Research Projects Agency (University Research Initiative) for partial financial support.

References

1. (a) Polak, A. J.; Petty-Weeks, S.; Beuhler, A. J. *Sensors and Actuators* **1986**, *9*, 1; (b) Petty-Weeks, S.; Polak, A. J. *Sensors and Actuators* **1987**, *11*, 377; (c) Petty-Weeks, S.; Zupancic, J. J.; Swedo, J. R. *Solid State Ionics* **1988**, *31*, 117.
2. (a) Pickup, P. G.; Murray, R. W. *J. Electrochem. Soc.* **1984**, *131*, 833; (b) Pickup, P. G.; Kutner, W.; Leidner, C. R.; Murray, R. W. *J. Am. Chem. Soc.* **1984**, *106*, 1991; (c) Abruna, H. D.; Denisevich, P.; Umana, M.; Meyer, T. J.; Murray, R. W. *J. Am. Chem. Soc.* **1981**, *103*, 1; (d) Denisevich, P.; Wildman, K. W.; Murray, R. W. *J. Am. Chem. Soc.* **1981**, *103*, 4727.
3. Kittlesen, G. P.; White, H. S.; Wrighton, M. S. *J. Am. Chem. Soc.* **1985**, *107*, 7373.
4. (a) White, H. S.; Kittlesen, G. P.; Wrighton, M. S. *J. Am. Chem. Soc.* **1984**, *106*, 5375; (b) Kittlesen, G. P.; White, H. S.; Wrighton, M. S. *J. Am. Chem. Soc.* **1984**, *106*, 7389; (c) Natan, M. J.; Mallouk, T. E.; Wrighton, M. S. *J. Phys. Chem.* **1987**, *91*, 648; (d) Paul, E. W.; Ricco, A. J.; Wrighton, M. S. *J. Phys. Chem.* **1985**, *89*, 1441; (e) Wrighton, M. S.; Chao, S.; Chyan, O. M.; Jones, E. T. T.; Leventis, N.; Lofton, E. P.; Schloh, M. O.; Shu, C. F. *Chemically Modified Microelectrode Surfaces in Science and Industry*; Leyden, D. E.; Collins, W. T., Eds.; Gordon and Breach: New York, **1987**; p. 337; (f) Natan, M. J.; Wrighton, M. S. *Progress in*

Inorganic Chemistry; Vol 37, Lippard, S. J., Ed.; John Wiley & Sons: New York, **1989**; p. 391-494.

5. Chao, S. C.; Wrighton, M. S. *J. Am. Chem. Soc.* **1987**, **109**, 2197.

6. Chao, S. C.; Wrighton, M. S. *J. Am. Chem. Soc.* **1987**, **109**, 6627.

7. Talham, D. R.; Crooks, R. M.; Cammarata, V.; Leventis, N.; Schloh, M. O.; Wrighton, M. S. *Lower-Dimensional Systems and Molecular Electronics*; Proceedings of NATO ASI, Spetses, Greece, 1989, Metzger, R. M.; Day, P.; Papavassiliou, G., Eds.; Plenum Press, in press.

8. (a) Rauh, R. D.; Cogan, S. F. *Solid State Ionics* **1988**, **28-30**, 1707; (b) Nguyen, M. T.; Dao, L. H. *J. Electrochem. Soc.* **1989**, **7**, 2131.

9. Schloh, M. O.; Leventis, N.; Wrighton, M. S. *J. Appl. Phys.* **1989**, **66**, 965.

10. (a) Bruce, P. G. *Polymer Electrolyte Reviews-1*; MacCallum, J. R.; Vincent, C. A., Eds.; Elsevier Applied Science: London, **1987**; p. 237; (b) Ratner, M. A.; Shriver, D. F. *Chem. Rev.*, **1988**, **88**, 109.

11. Lofton, E. P.; Thackeray, J. W.; Wrighton, M. S. *J. Phys. Chem.* **1986**, **90**, 6080.

Table I. Rectification factors of the WO_3 /polyaniline-based diodes in poly(vinyl alcohol)/ H_3PO_4 solid electrolyte as a function of frequency. I_f and I_r correspond to +1.0 V and -1.0 V biasing respectively.

Frequency (Hz)	I_f (μA)	I_r (μA)	I_f/I_r
steady state	640	1.5	427
0.0125 (l)	705	14	14.9
0.025 (l)	570	45	12.7
0.125 (l)	560	55	10.2
0.50 (l)	520	55	9.5
1.0 (s)	525	60	8.8
1.25 (l)	465	55	8.5
5 (s)	135	45	3.0
10 (s)	135	55	2.5
100 (s)	145	95	1.5
1000 (s)	70	50	1.4

(l): linear sweep.

(s): sinusoidal sweep.

FIGURE CAPTIONS

Figure 1. Element distribution as seen by the scanning Auger microprobe. **A:** SEM picture obtained with the electron microprobe of the Auger spectrometer at 1500X magnification; **B:** Tungsten map; **C:** Silicon map; **D:** Platinum map.

Figure 2. Scanning Auger microprobe surveys. **A:** on WO_3 ; **B:** on an underivatized Pt microelectrode; **C:** on the trench between the array and the Pt protective barrier.

Figure 3. AC impedance spectra of poly(vinyl alcohol)/ H_3PO_4 film in (A) hydrated "wet" Ar atmosphere and (B) dry Ar atmosphere. The highest frequency used is 100 kHz (extreme left point) and the low frequency is 1 Hz (extreme right point). The ionic resistance of the dry polymeric electrolyte is $R = 2.2 \times 10^6 \Omega$ for the impedance cell used. The resistance of the polymeric electrolyte drops to $R = 800 \Omega$ in the hydrated state.

Figure 4. Optical micrographs of (top) a "self referencing" WO_3 and polyaniline device, where WO_3 and polyaniline are not in contact with each other, and (bottom) a WO_3 /polyaniline diode with a physical connection between the two materials.

Figure 5. Cyclic voltammetry of polyaniline and WO_3 confined on an eight microelectrode array vs. a Ag quasi-




reference electrode. The device is covered by a thin film of poly(vinyl alcohol)/H₃PO₄ solid electrolyte and kept in a H₂O-saturated Ar atmosphere.

Figure 6. Switching characteristics of WO₃ and polyaniline on the same chip addressed independently.

Figure 7. Switching characteristics of WO₃ and polyaniline on the same chip referenced one vs. the other.

Figure 8. Steady-state two terminal current-voltage characteristic of a WO₃/polyaniline device with (•) hardwire connection between the redox materials and without (○) hardwire connection.


Figure 9. Plot of the current, I , and applied potential, V , vs. time at 1 Hz frequency for a WO₃/polyaniline-based diode operated at 298 K in poly(vinyl alcohol)/H₃PO₄ solid electrolyte. The variation in V is from -1.0 V ($I = 0$) to +1.0 V ($I > 0$). $I_{\text{forward}}/I_{\text{reverse}} = 8.8$.

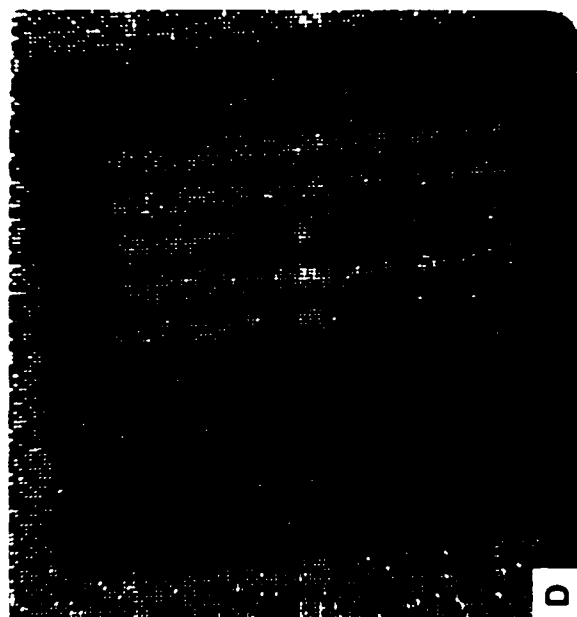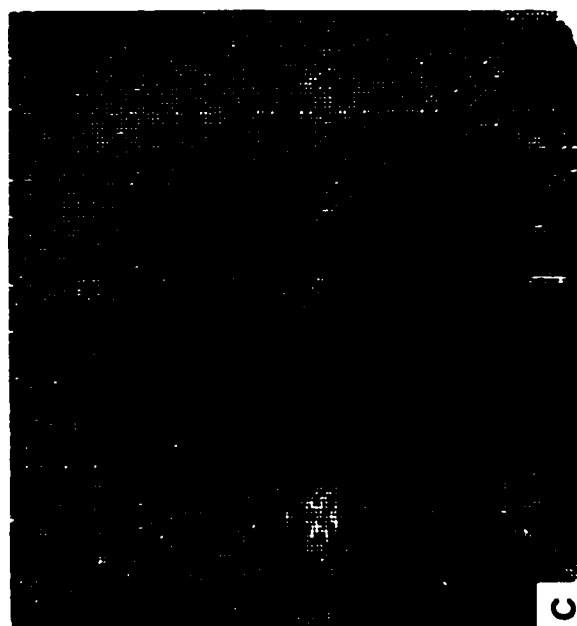
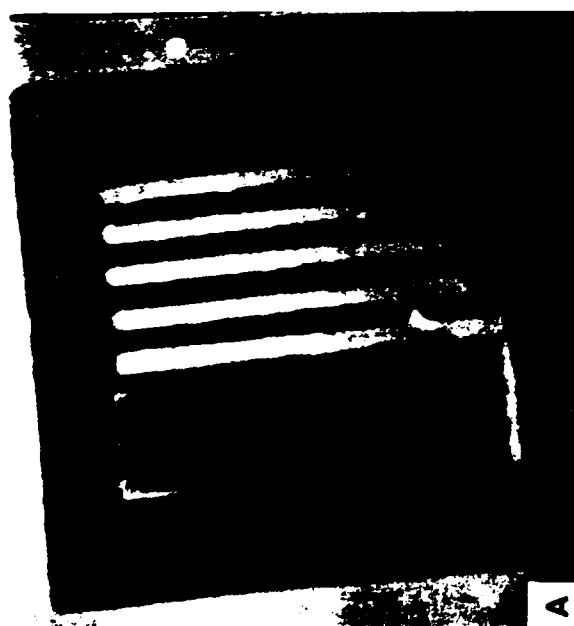


10 μ m

10 μ m

Auger Surveys of a WO_3 Derivatized Microelectrode Array

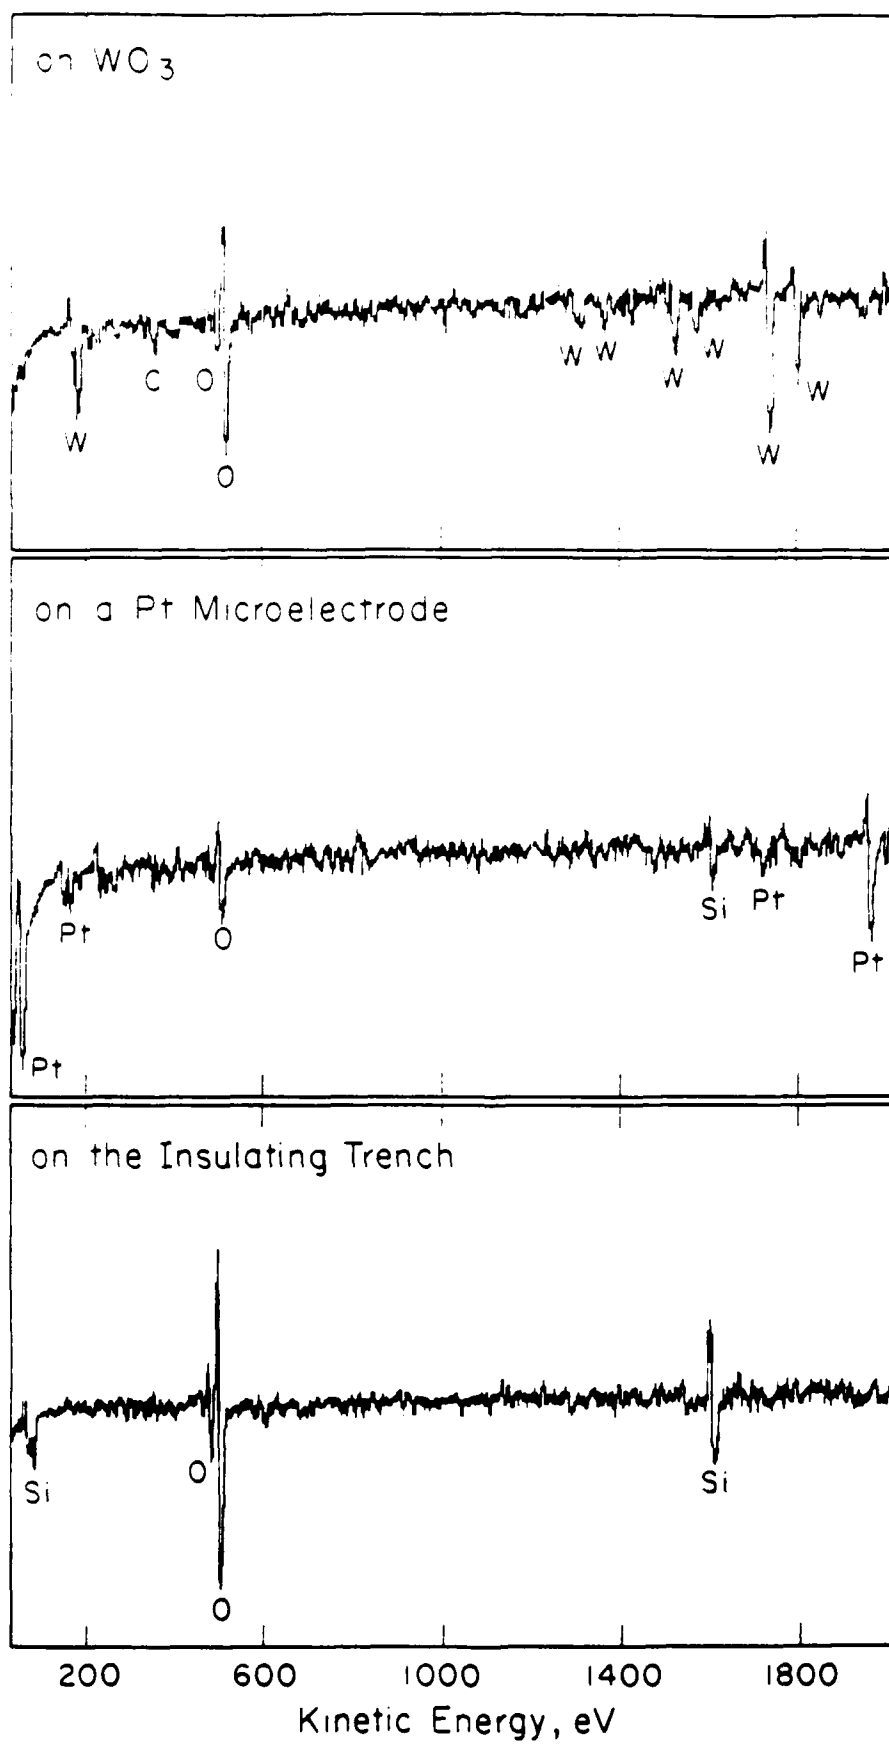

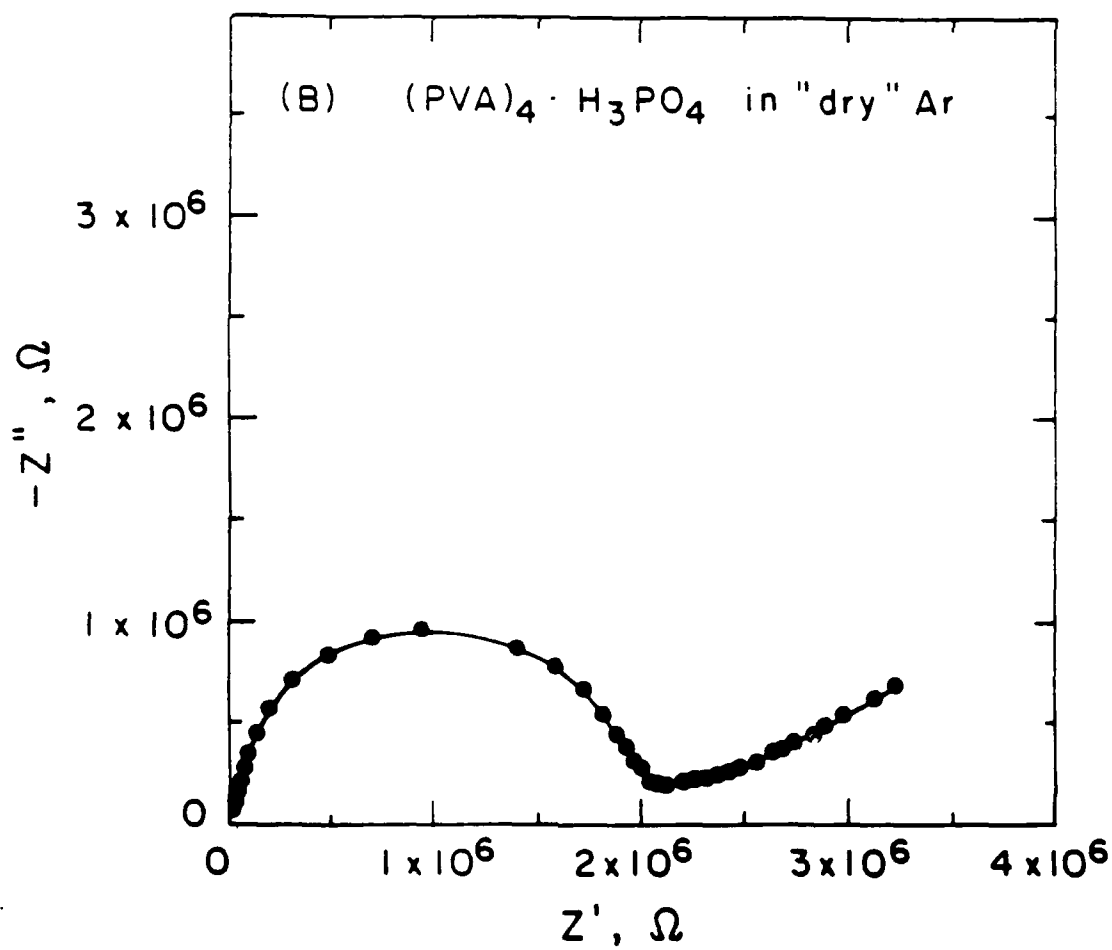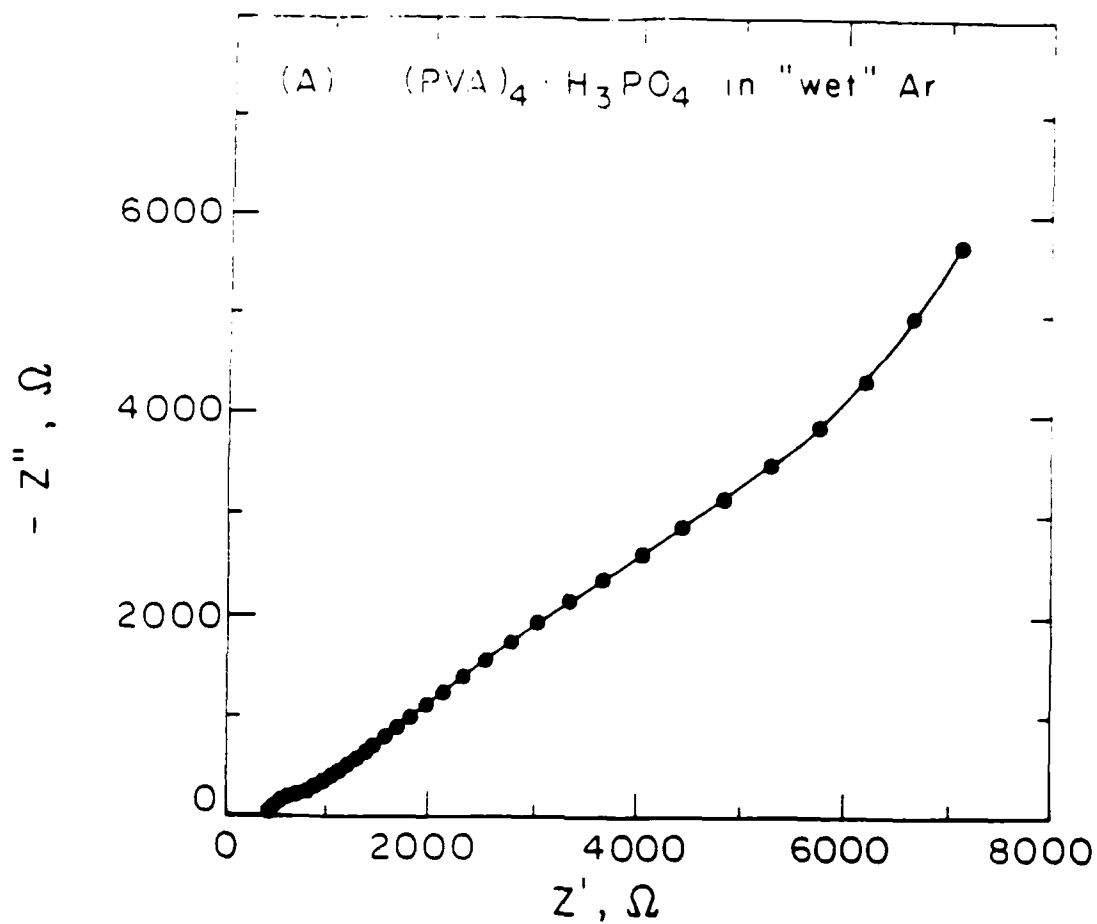


"Self Referencing" WO_3 and Polyaniline
Based Transistors




WO_3 /Polyaniline - Based Microelectrochemical
Diode





Cyclic Voltammetry of a Microelectrode Array Carrying Polyaniline over two Wires and WO_3 over three Wires in Polyvinylalcohol / H_3PO_4 Solid Electrolyte

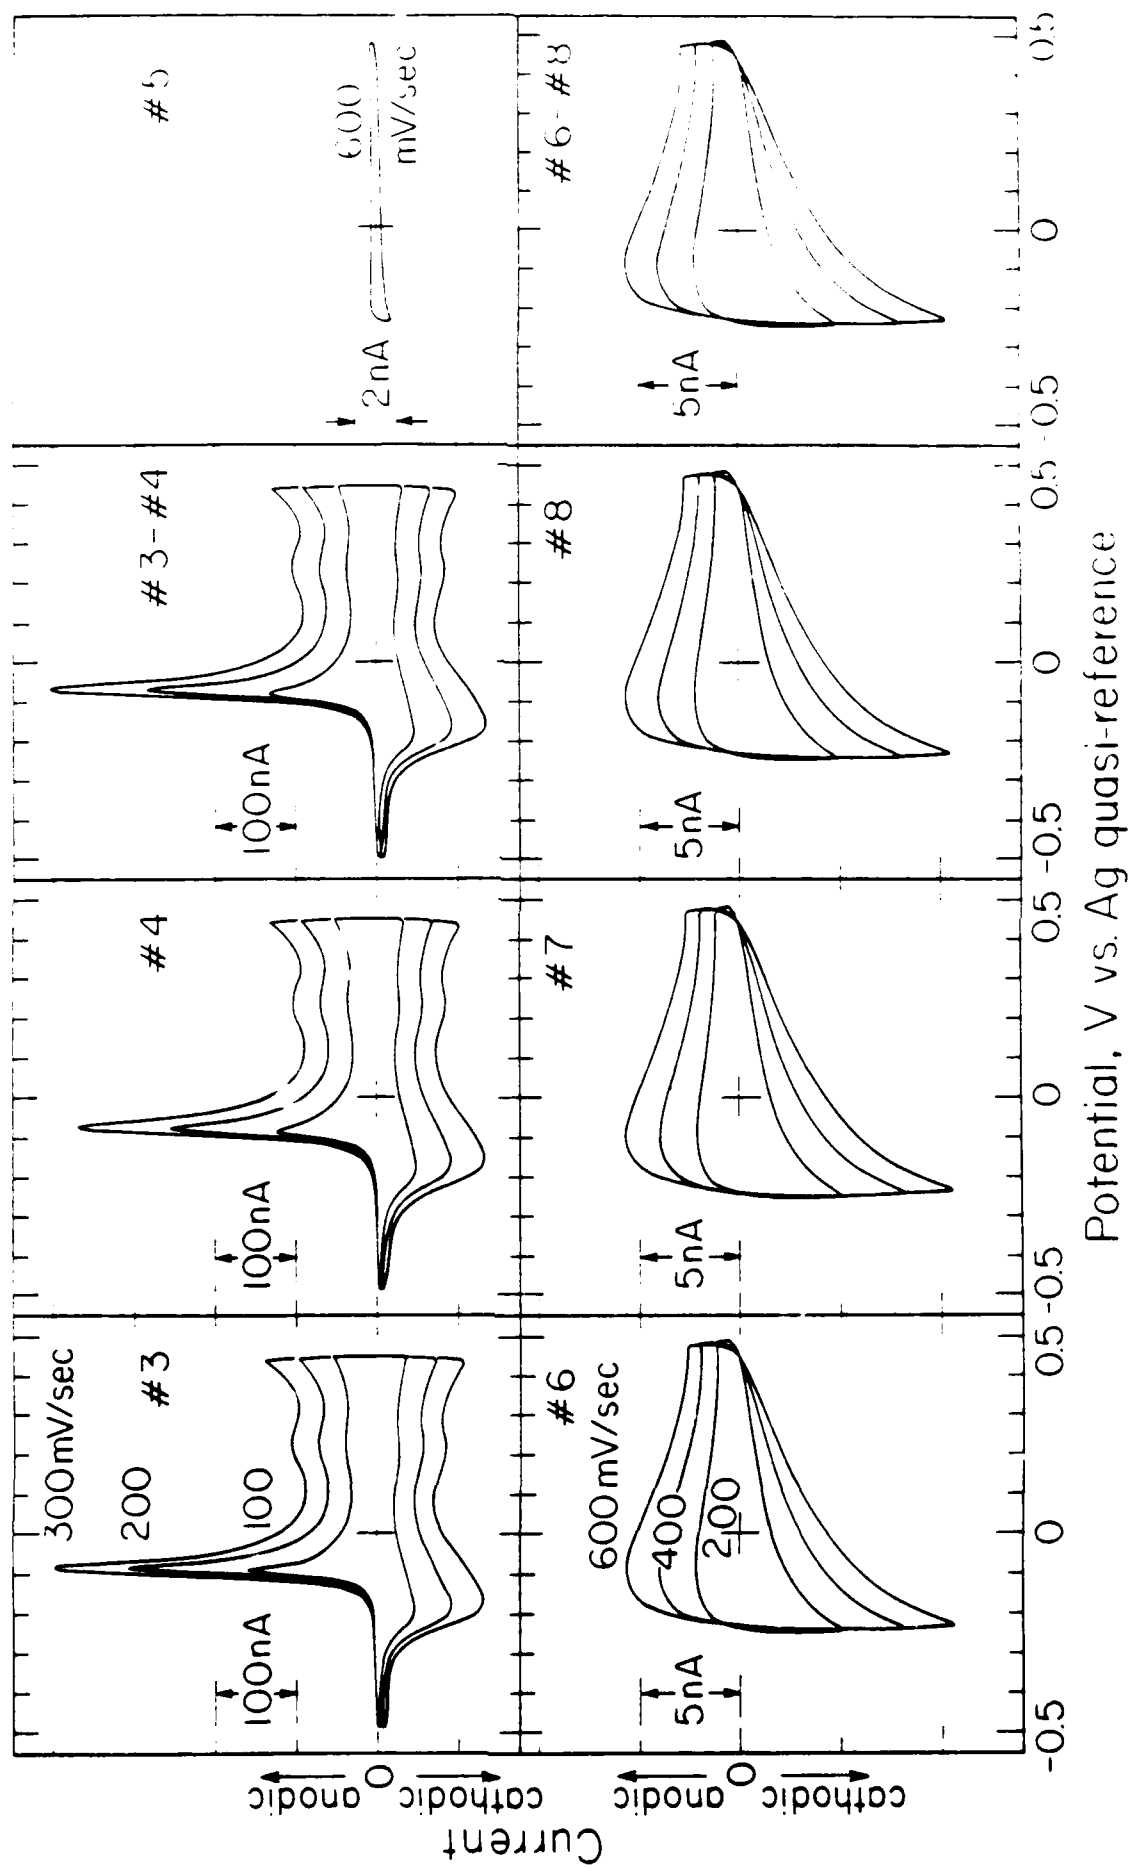


Independent Characterization of WO_3 (\square) and
Polyaniline (\bullet) Based Transistors in
Polyvinylalcohol / H_3PO_4 Solid Electrolyte

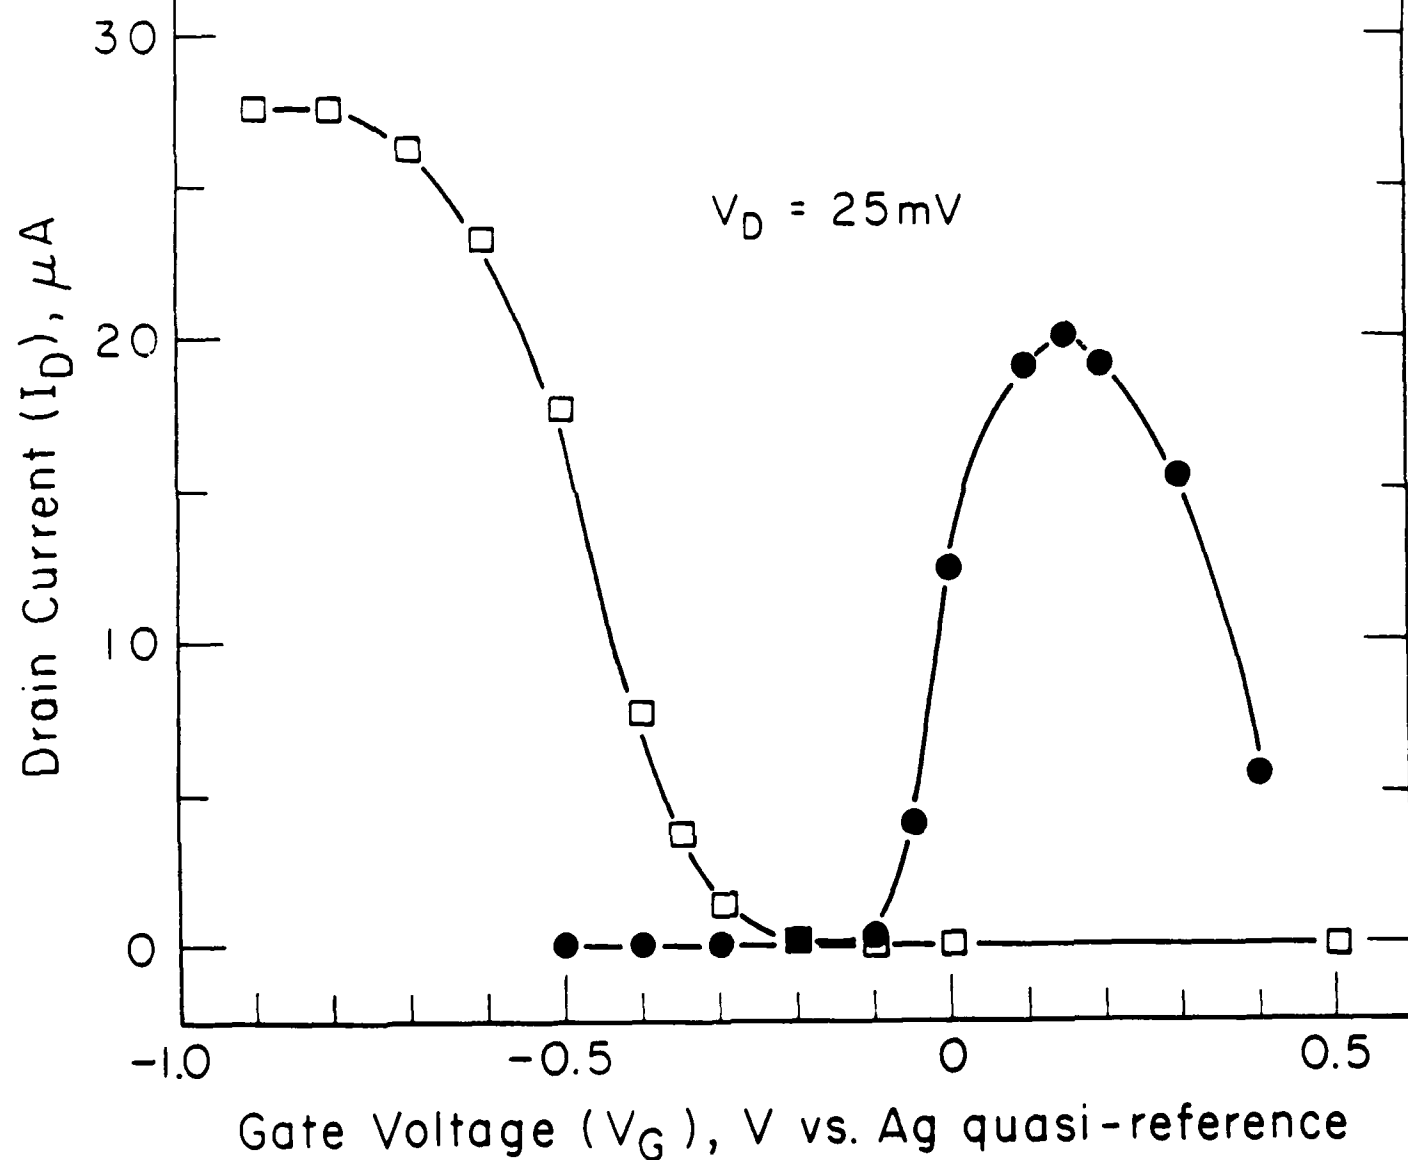

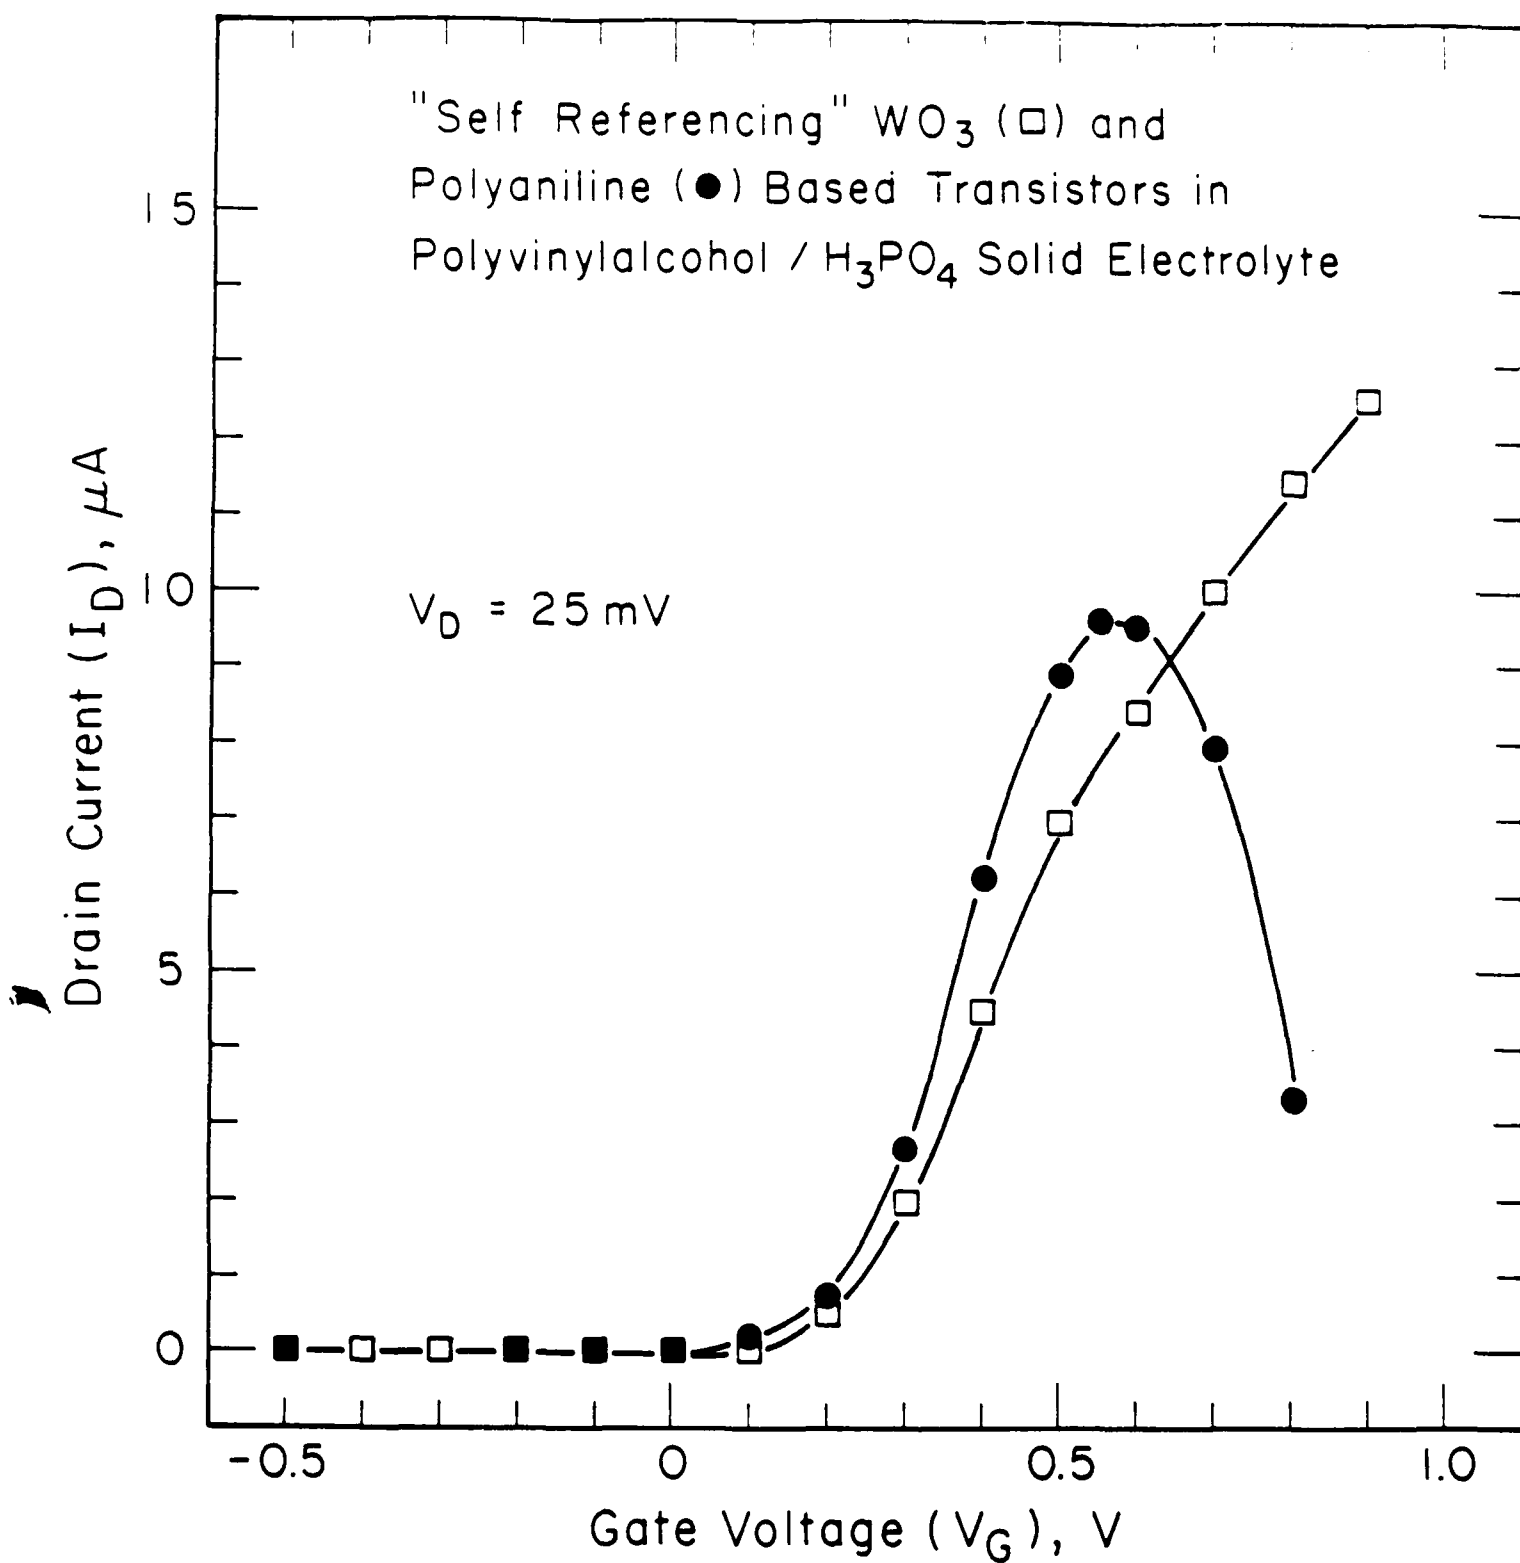

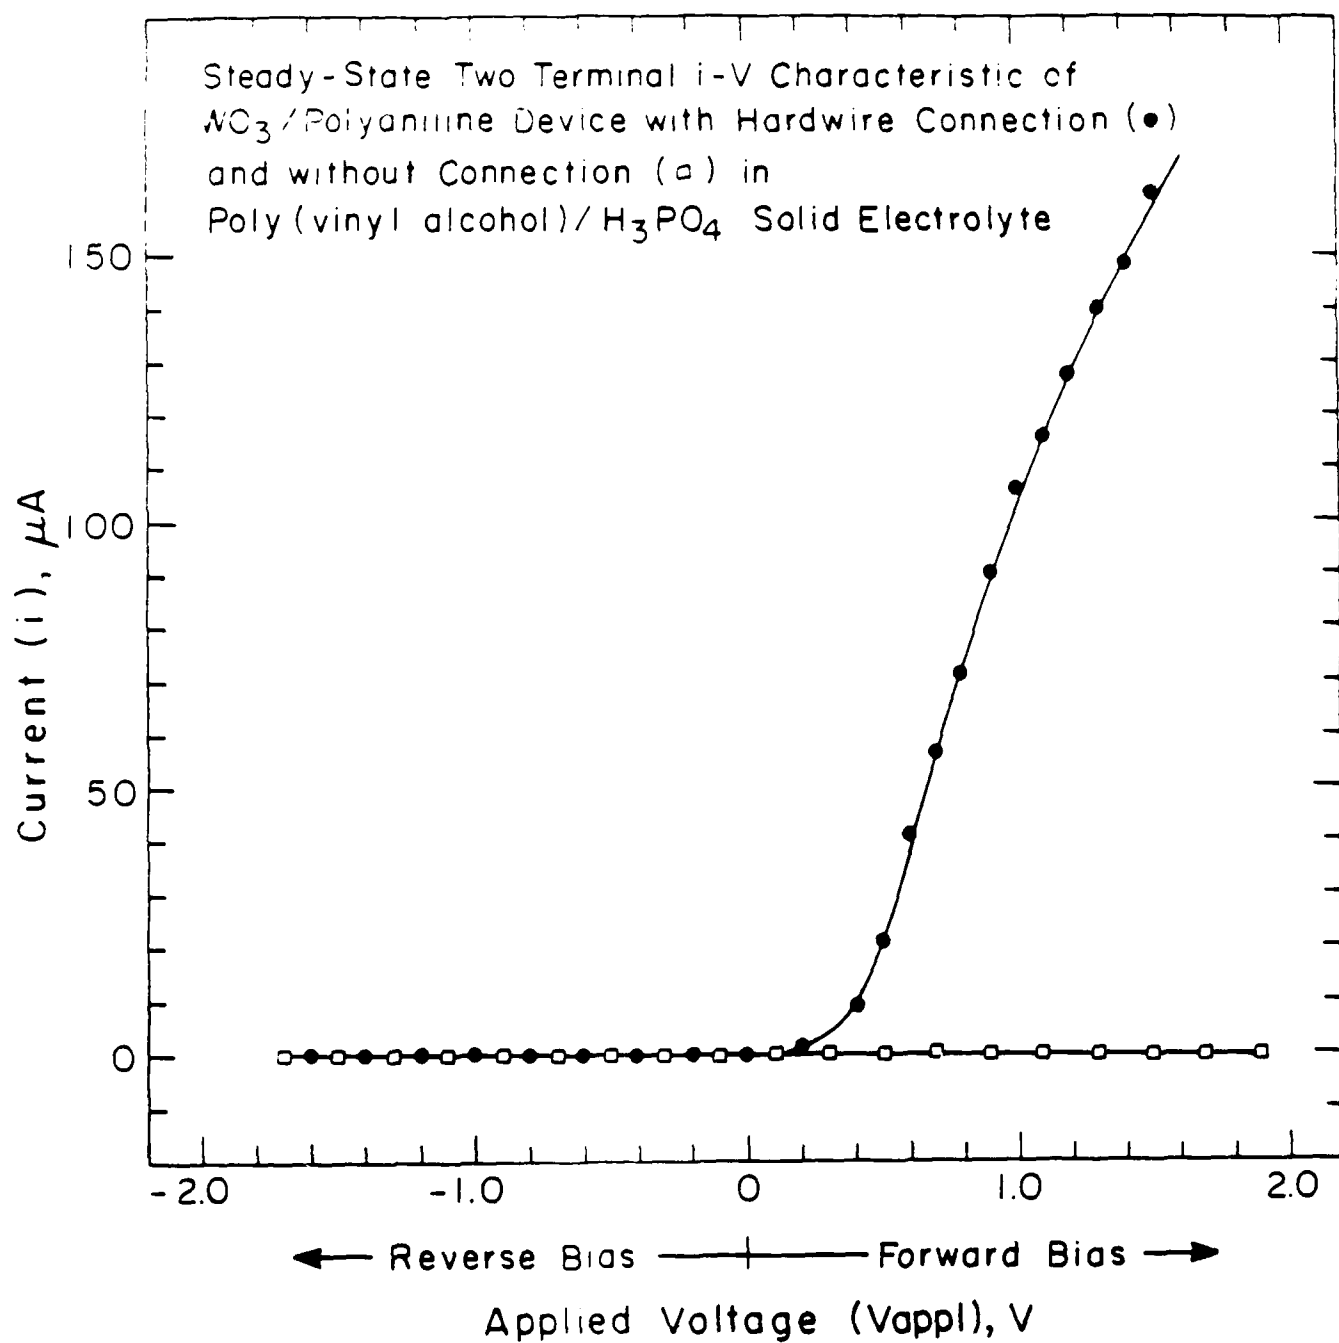

Time Dependence of a WO_3 /Polyaniline-Based Microelectrochemical Diode

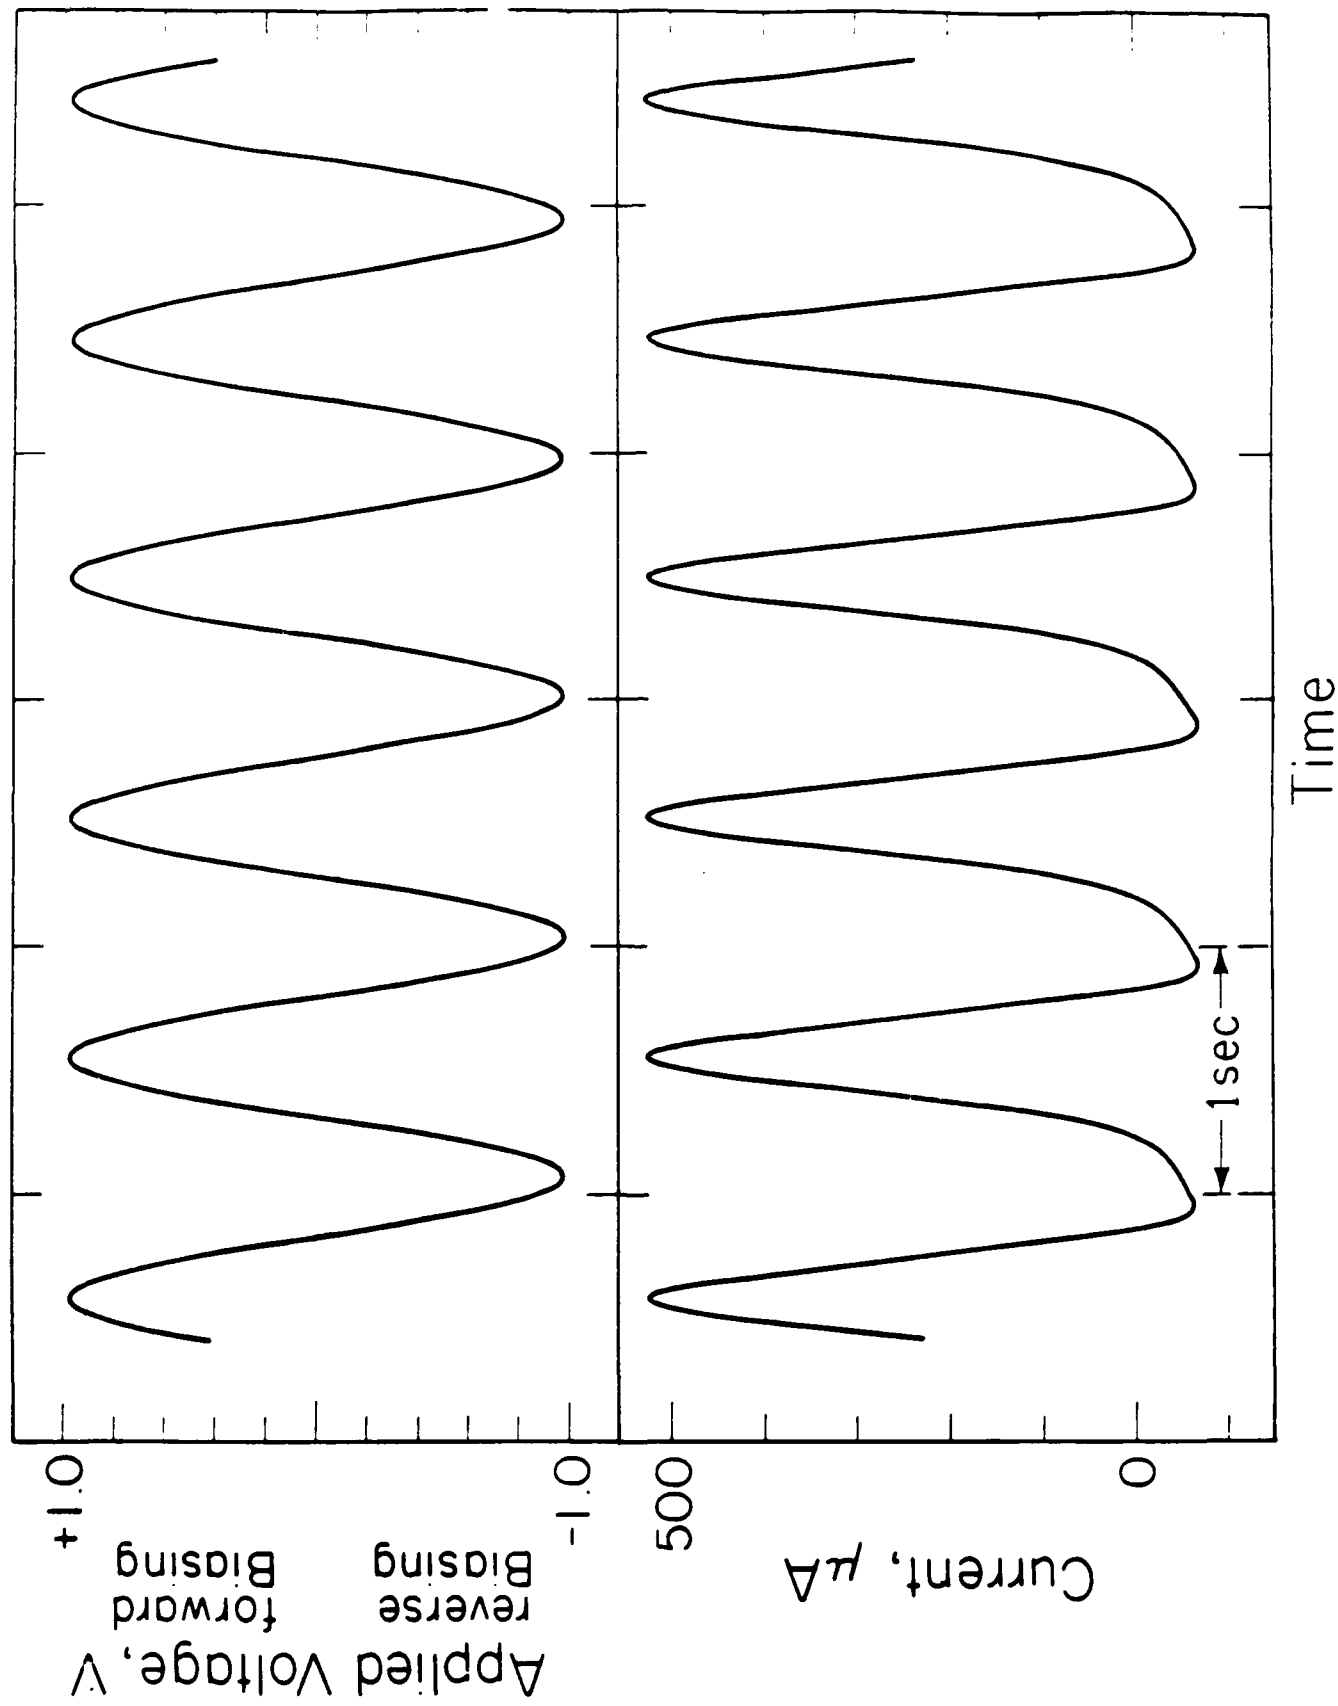

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)
Chemistry Division, Code 1113
800 North Quincy Street
Arlington, Virginia 22217-5000

Commanding Officer (1)
Naval Weapons Support Center
Dr. Bernard E. Douda
Crane, Indiana 47522-5050

Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043

David Taylor Research Center (1)
Dr. Eugene C. Fischer
Annapolis, MD 21402-5067

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)
Chemistry Division, Code 385
Naval Weapons Center
China Lake, CA 93555-6001

Chief of Naval Research (1)
Special Assistant for Marine
Corps Matters
Code 00MC
800 North Quincy Street
Arlington, VA 22217-5000

Dr. Bernadette Eichinger (1)
Naval Ship Systems Engineering
Station
Code 053
Philadelphia Naval Base
Philadelphia, PA 19112

Dr. Sachio Yamamoto (1)
Naval Ocean Systems Center
Code 52
San Diego, CA 92152-5000

Dr. Harold H. Singerman (1)
David Taylor Research Center
Code 283
Annapolis, MD 21402-5067

ENCLOSURE(2)